

# LIDT TEST RESULTS

## LIDT VALUE

$10^3$ -on-1

$55.8^{+3.9}_{-13.2}$  J/cm<sup>2</sup>

## CHARACTERISTIC DAMAGE CURVE

Table 1: Estimated LIDTs from fitting model for sample AR1064\_pasl.

Test mode	Threshold (Offline detection - microscopy)	Threshold (Online detection - scattering)
1-on-1	$55.8^{+4.9}_{-13.2}$ J/cm <sup>2</sup>	$56.0^{+5.0}_{-10.9}$ J/cm <sup>2</sup>
10-on-1	-	$56.0^{+3.8}_{-10.9}$ J/cm <sup>2</sup>
$10^2$ -on-1	-	$56.0^{+3.8}_{-10.9}$ J/cm <sup>2</sup>
$10^3$ -on-1	$55.8^{+3.9}_{-13.2}$ J/cm <sup>2</sup>	$55.8^{+3.9}_{-13.2}$ J/cm <sup>2</sup>

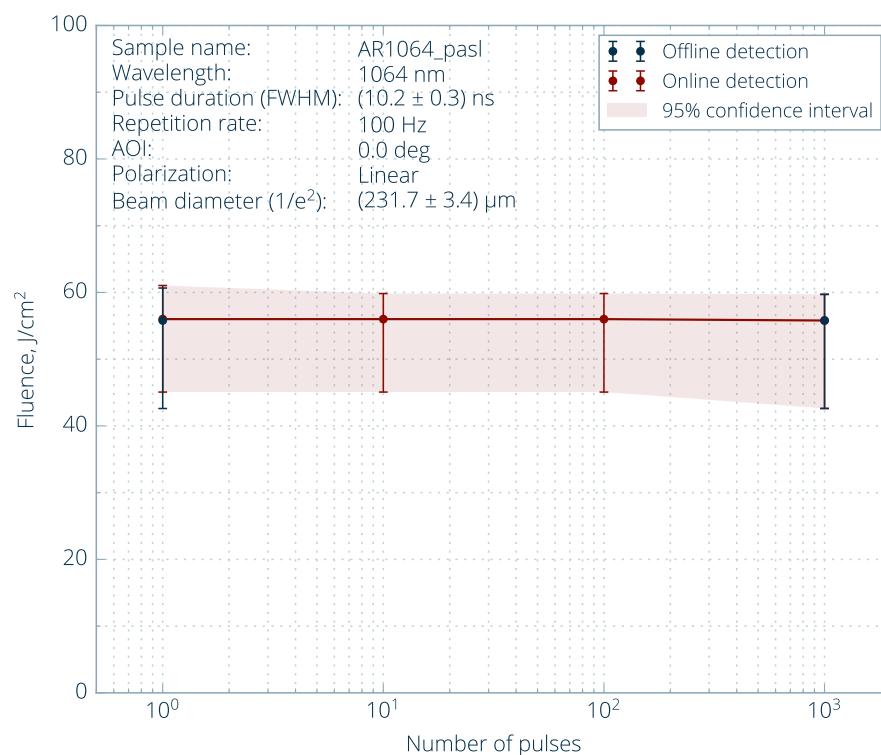


Figure 2. Characteristic damage curve.